

Iron Oxide Nanoparticles Modified with Carbon Quantum Nanodots for the Stabilization of Palladium Nanoparticles: An Efficient Catalyst for the Suzuki Reaction in Aqueous Media under Mild Conditions

Mohammad Gholinejad,^{*,[a]} Mohammed Seyedhamzeh,^[a] Mehran Razeghi,^[a] Carmen Najera,^{*,[b]} and Mohsen Kompany-Zareh^[a]

Magnetic Fe₃O₄ nanoparticles (NPs) functionalized with carbon dots (C-dots) that contain carboxylic acid and hydroxyl groups were synthesized successfully and used for the reduction of Pd^{II} and the formation of Pd NPs. The new material was characterized by SEM, TEM, energy-dispersive spectroscopy, solid UV spectroscopy, vibrating sample magnetometry, XRD, and X-ray photoelectron spectroscopy and was used as a very efficient catalyst in the Suzuki–Miyaura cross-coupling reaction of aryl bromides and chlorides with arylboronic acids in aqueous

media. Design of experiments indicates that the use of 0.22 mol% of Pd, K₂CO₃ as the base, and aqueous ethanol are the best reaction conditions. The reactions of aryl bromides take place at room temperature, and aryl chlorides react at 80 °C. The easily synthesized and air-stable catalyst Pd@C-dots@Fe₃O₄ NPs could be separated from the reaction mixture by using an external magnet and reused in eight consecutive runs with ■■no significant loss of■■ catalytic activity.

Introduction

■■Change to title ok?■■Pd-catalyzed cross-coupling reactions are very important and powerful strategies for the formation of C–C and C–heteroatom bonds.^[1] As a result of the toxicity and high price of Pd, in recent years, interest has grown in the organization and use of recoverable heterogeneous Pd catalysts.^[2] For this purpose, different solid materials such as modified silicas,^[3] polymers,^[4] mesoporous materials,^[5] ionic liquids,^[6] and natural supports^[7] have been designated as supports for the heterogenization of Pd catalysts. Even with significant achievements in this area, the separation and efficient recovery of the heterogeneous catalyst from the reaction medium by conventional methods such as filtration or centrifugation is not always an easy assignment. One of the best methods to solve this problem is the use of magnetic nanoparticles (NPs) of Fe₃O₄ as a very convenient support for heterogenization of Pd catalysts.^[8] Very simple isolation and recovery, high surface area, and low toxicity are the key advantages of magnetic-NP-supported catalysts.

Recently, carbon quantum nanodots (C-dots) have been described as a new class of carbon structures with interesting properties. They are green, nontoxic, abundant, and inexpensive materials. In addition, C-dots have unique properties such as photostability and fluorescence emission, and for these reasons have been considered in different applications such as biosensing, bioimaging, light emitting diodes, fluorescent ink, and photocatalysis.^[9,10] Different methods such as laser ablation, pyrolysis, wet oxidation, ultrasound- and microwave-assisted synthesis, hydrothermal synthesis, and electrochemical etching have been developed for the synthesis of C-dots.^[8,9] The carboxylic and hydroxyl moieties of the C-dots confer excellent water solubility as well as biocompatibility and give them promise as an excellent support for catalyst stabilization. However, compared to other carbon structures such as carbon nanotubes and graphene,^[11] less attention has been paid to the use of C-dots as solid supports for catalysis design. Recently, C-dots-reduced Pd NPs have been reported as an efficient catalyst in Suzuki and Heck coupling reactions in water.^[12] However, to the best of our knowledge, there are no reports that deal with the modification of Fe₃O₄ NPs using C-dots and its application for stabilization of Pd NPs. In continuation of our interest into magnetically separable heterogeneous Pd catalysts,^[13] herein, we wish to report for the first time the synthesis and characterization of Pd NPs supported on magnetite NPs modified with C-dots and its application as a sustainable catalyst in the Suzuki–Miyaura cross-coupling reaction in aqueous media.

[a] M. Gholinejad, M. Seyedhamzeh, M. Razeghi, M. Kompany-Zareh
Department of Chemistry, Institute for Advanced Studies in Basic Sciences (IASBS)

P. O. Box 45195-1159, Gavazang, Zanjan 45137-6731 (Iran)
E-mail: gholinejad@iasbs.ac.ir

[b] Prof. C. Najera
Departamento de Química Orgánica and Centro de Innovación en Química Avanzada (ORFEO-CINQA), Universidad de Alicante
Apdo. 99, E-03080-Alicante (Spain)
E-mail: cnajera@ua.es

Supporting Information for this article is available on the WWW under <http://dx.doi.org/10.1002/cctc.201500925>.

Results and Discussion

Fe₃O₄ NPs were prepared in a coprecipitation step based on the procedure of Massart using FeCl₃·6H₂O and FeCl₂·4H₂O.^[14] C-dots were prepared following a procedure described previously using a mixture of citric acid and urea that was transferred to a Teflon autoclave and heated at 160 °C for 6 h.^[15a] The obtained C-dots were treated with Fe₃O₄ NPs at 60 °C for 24 h to afford C-dots@Fe₃O₄ NPs. The final Pd@C-dots@Fe₃O₄ catalyst was obtained simply by dissolving PdCl₂ in water by sonication and the addition of C-dots@Fe₃O₄, also dissolved in water by sonication, and heating at 60 °C for 1 day. The loading of Pd in the obtained material was determined by inductively coupled plasma (ICP) analysis to be 0.27 mmol g⁻¹. Thermogravimetric analysis (TGA) of the prepared material showed two major weight losses between 25 and 700 °C. The first weight loss, which occurs between 25 and 100 °C, is related to water and physically adsorbed solvents. The second weight loss, which occurred between 100 and 700 °C, may be related to the C-dots on the Fe₃O₄ NPs (Figure 1).

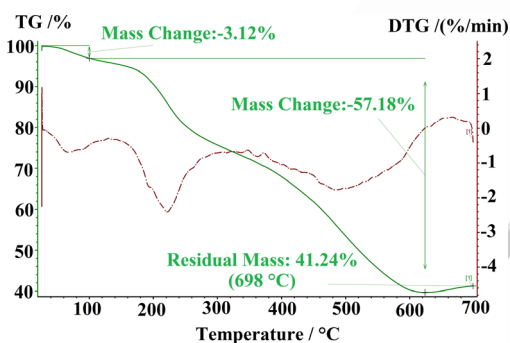


Figure 1. TGA profile of Pd@C-dots@Fe₃O₄.

FTIR spectroscopy provided further confirmation that the surface of the magnetic NPs was modified by C-dots (Figure 1, Supporting information). The absorption bands at $\tilde{\nu}$ = 3000–3500 cm⁻¹ are assigned to the stretching vibrations of OH and NH₂ groups, and a peak at $\tilde{\nu}$ = 1622 cm⁻¹ can be assigned to the C=O band.

XRD analysis of the prepared material showed the formation of Pd⁰ NPs on the C-dot@Fe₃O₄ surface by the appearance of Bragg's reflections related to Fe₃O₄ NPs^[16] at 2θ = 30.17, 35.46, 43.38, 53.69, 57.23, and 62.77° and those related to Pd NPs^[17] at 2θ = 40.1, 46.7, and 68.1° (Figure 2).

The reduction of Pd^{II} to Pd⁰ was also confirmed by diffuse reflectance UV/Vis (DR UV/Vis) spectroscopy from the disappearance of the peak related to PdCl₂ at λ = 280 nm in the spectrum of Pd@C-dots@Fe₃O₄ (Figure 3).^[18]

However, to obtain exact information about the oxidation state of Pd species, X-ray photoelectron spectroscopy (XPS) was performed (Figure 4). Results showed the presence of an intense doublet at a binding energy (BE) of 335.6 and 340.8 eV related to Pd⁰ and peaks at BE = 338 and 343 eV related to Pd^{II}, which correspond to the Pd3d_{5/2} and Pd3d_{3/2} peaks, respec-

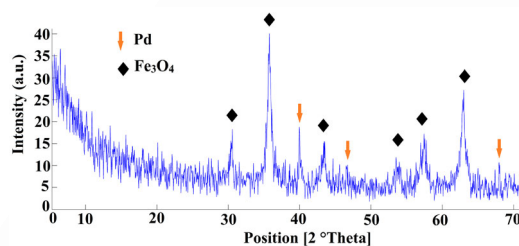


Figure 2. XRD pattern of Pd@C-dots@Fe₃O₄.

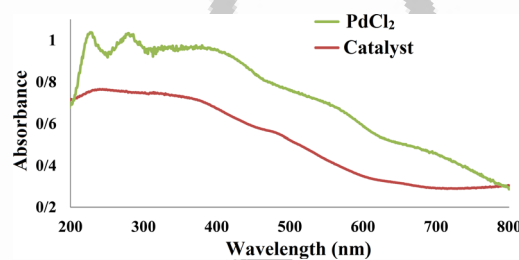


Figure 3. DR UV/Vis spectra of PdCl₂ and Pd@C-dots@Fe₃O₄.

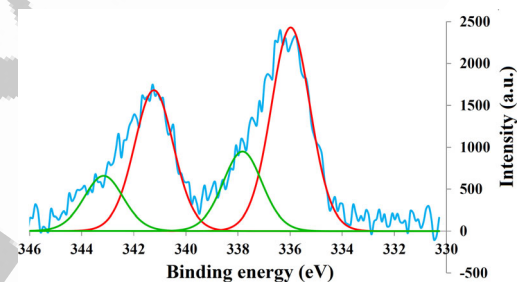


Figure 4. XPS spectrum of Pd@C-dots@Fe₃O₄ in the Pd 3d region.

tively. These results indicate that most of the Pd is present in the reduced form, which confirms the capability of C-dots@Fe₃O₄ in the efficient reduction of Pd^{II} to Pd⁰ NPs.^[19]

Moreover, the presence of carbon in the structure of Pd@C-dots@Fe₃O₄ confirmed by XPS analysis by the appearance of peaks related to C 1s at BE = 283.87 eV for graphitic or aliphatic carbon, BE = 286.13 eV for oxygenated carbon, and BE = 287.75 eV for nitrous forms of carbon (Figure 5).^[15]

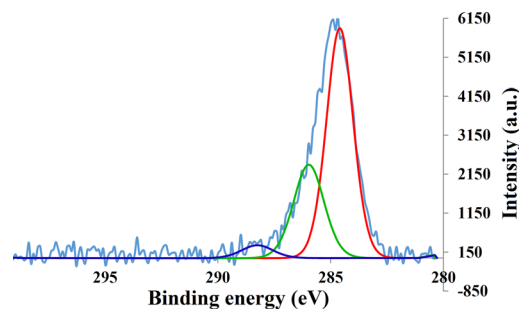


Figure 5. XPS spectrum of Pd@C-dots@Fe₃O₄ in the C 1s region.

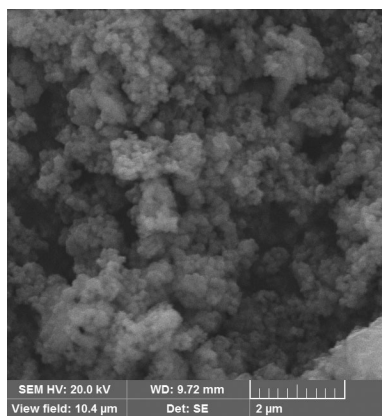


Figure 6. SEM image of Pd@C-dots@Fe₃O₄.

SEM images of the Pd@C-dots@Fe₃O₄ showed the formation of uniform spherical particles (Figure 6), and the energy-dispersive spectrum (EDS) obtained from SEM confirmed the presence of Pd, Fe, and C species in the structure of the material (Figure 7). Furthermore, TEM images of the material at different magnifications showed the nanostructure character of the prepared material of an average size of 20 nm and showed the presence of carbon shells in the structure (Figure 8).

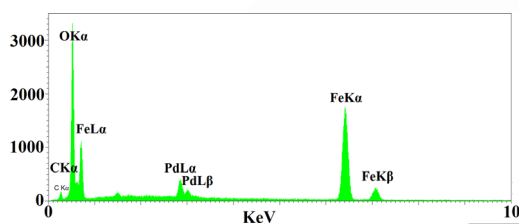


Figure 7. EDS spectrum of Pd@C-dots@Fe₃O₄ obtained from SEM.

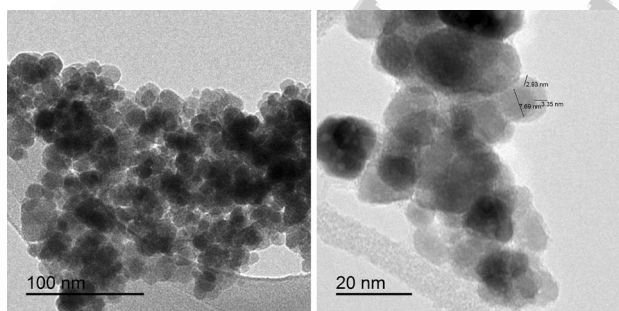


Figure 8. TEM image of Pd@C-dots@Fe₃O₄ at different magnifications.

The superparamagnetic character of Pd@C-dots@Fe₃O₄ and Fe₃O₄ NPs was also studied. Results showed that the decrease in the magnetization value of the Pd@C-dots@Fe₃O₄ (50 emu g⁻¹) in comparison with that of Fe₃O₄ NPs (64 emu g⁻¹) confirms the modification of Fe₃O₄ NPs with C-dots (Figure 9). Zero coercivity, remanence on the mag-

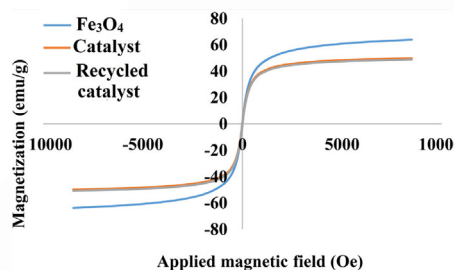


Figure 9. Magnetization values.

netization loop, and the absence of a hysteresis loop in both samples confirmed the superparamagnetic properties and the ease of separation of the material from the reaction mixture.

The catalytic activity of the prepared Pd@C-dots@Fe₃O₄ was evaluated in the Suzuki–Miyaura coupling reaction of aryl bromides and chlorides. To find the optimized reaction conditions, design of experiments (DoE)^[20] for the reaction of 4-bromoanisole and phenylboronic acid as a model reaction was pursued. A five-level, three-factor central composite design to study of the effect of the parameters on coupling reaction was created (Table S1). The three independent variables (factors) are the solvent type (X_1), base type (X_2), and the amount of catalyst (X_3). The regression coefficients obtained from the mathematical linear second-order model [Eq. (1), Supporting Information] are given in Table S2. From the results of Table S2, a second-order mathematical model [Eq. (2)] was generated. After we substituted regression coefficients into Equation (1), a new equation that involved Y (reaction yield), X_1 , X_2 , and X_3 was obtained.

$$Y = 89.8515 + 7.2724 X_1 + 2.3165 X_2 + 2.3764 X_3 + 6.6250 X_1 X_2 - 0.3750 X_1 X_3 - 1.1250 X_2 X_3 - 29.9348 X_1^2 - 28.6974 X_2^2 - 1.1202 X_3^2 \quad (2)$$

We used statistical analysis of variance (ANOVA) significance and fitness of the model as well as the effects of significant individual terms and their interactions to study the chosen responses (Tables S2 and S3).

Usually, the parameters with $p < 0.05$ are considered as significant parameters, and a correlation factor $R^2 > 0.85$ is desired for the mathematical model to be considered as a good approximation of the reaction. The type of solvent, quadratic term of the solvent, quadratic term of the base, and solvent–base interaction term were significant model terms (Table S2). The results show that the effect of the type of solvent is dependent on the type of base applied in the reaction. In addition, the effects of catalyst and the quadratic term of catalyst–base and catalyst–solvent interactions were insignificant. The insignificant effect of catalysis does not mean that catalysis has no effect on the reaction rate. It means that a change in concentration of the catalyst has no significant effect compared to that of the type of solvent and applied base. Insignificant terms can be removed from the model manually to improve the regression model and optimization results [Eq. (3)].

$$Y = 89.8515 + 7.2724 X_1 + 16.6250 X_1 X_2 - 0.3750 X_1 X_3 - 1.1250 X_2 X_3 - 29.9348 X_1^2 - 28.6974 X_2^2 \quad \text{Eq. (3)}$$

We used Equation (3) to plot a 3D graph of the second-order Suzuki coupling reaction (Figure 10). The yield of the reaction increased in the middle of the diagram (dark red), which indicates the use of EtOH/H₂O as the solvent and K₂CO₃ as the base. Furthermore, a contour plot diagram obtained from the 3D graph confirmed that the best reaction yield could be obtained using EtOH/H₂O as the solvent and K₂CO₃ as the base (Figure 11).

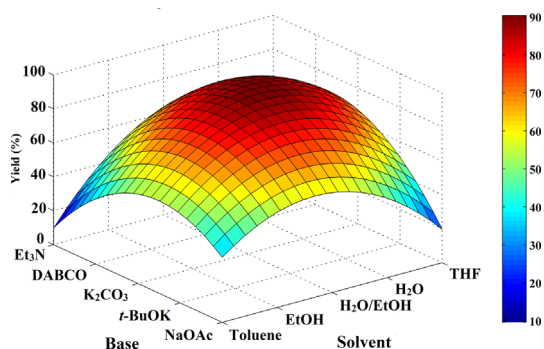


Figure 10. 3D graph of the second-order reaction to model the Suzuki coupling.

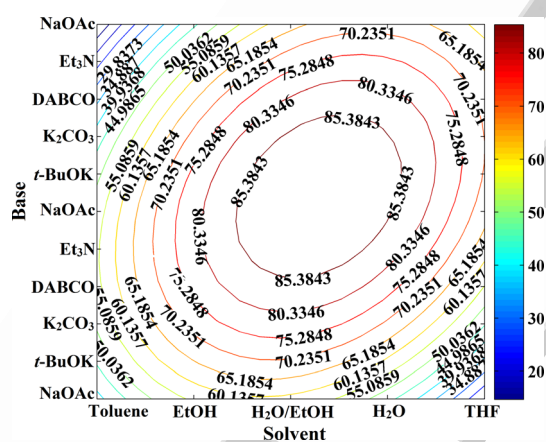


Figure 11. Contour plot diagram obtained from the 3D graph.

Notably, 3D graphs and their corresponding contour plots for the base with respect to the amount of catalyst and also the solvent with respect to the catalyst amount indicated that the use of 0.22 mol% of Pd, EtOH/H₂O as the solvent, and K₂CO₃ as the base are the best reaction conditions. The model reaction under the optimized reaction conditions was also studied without the catalyst, but only 3% conversion to the product was observed. Under the optimized reaction conditions, the reactions of structurally different aryl bromides and chlorides with different arylboronic acids were studied in the presence of the catalyst (Table 1). The results indicate that aryl bromides that contain electron-donating groups, such as 4-OH,

4-OMe, and 4-Me, as well as electron-withdrawing groups, such as 4-NO₂, 4-Cl, 4-CN, 4-CHO, and 2-CHO, with phenylboronic acid proceeded satisfactorily, and the corresponding coupling products were obtained in high to excellent yields (Table 1, entries 1–11). Moreover, reactions of unsubstituted aryl bromides, such as bromobenzene, bromobiphenyl, and 1-bromonaphthalene, proceed efficiently and afford the corresponding products (Table 1, entries 1, 12 and 13). The reaction of 5-bromopyrimidine as a heterocyclic aryl bromide with phenylboronic acid gave the coupling product in 98% isolated yield (Table 1, entry 2). Substituted aryl chlorides are less expensive than aryl bromides and more accessible for Pd-catalyzed cross-coupling reactions. However, the reactions of aryl chlorides under the optimized reaction conditions at room temperature were sluggish, therefore, the reaction temperature was increased to 80 °C. Under these reaction conditions, the Suzuki–Miyaura reaction was efficient, and the desired cross-coupling products were obtained in high to excellent yields (Table 1, entries 18–22).

To show the importance of the C-dots in the activation and stabilization of Pd NPs, a similar catalyst without C-dots was synthesized. Pd absorbed physically on Fe₃O₄ NPs was tested in the model reaction under the optimized reaction conditions. However, the results showed that reaction achieved only 14% GC yield in 24 h. This result confirms the key role of C-dots for the reduction and formation of reactive Pd NPs in the catalyst structure.

One of the main advantages of magnetite-NPs-supported catalysts is the easy separation and recycling of the catalyst. To study the recycling properties of this catalyst, the reaction of 5-bromopyrimidine with phenylboronic acid under the optimized reaction conditions was selected. The results showed that the catalyst is recyclable in eight consecutive runs just by decantation with a magnetic bar with no significant loss of catalytic activity (Figure 12).






















































Figure 12. Recycling experiments for the cross-coupling of 5-bromopyrimidine and phenylboronic acid.

The leaching of Pd into the reaction solution after eight runs was determined by ICP analysis to be 1.26%, which indicates the stability of the catalyst during the reaction. In addition, SEM (Figure 13) and TEM (Figure 14) images of the catalyst after the third run showed that the nanostructure of the catalyst was preserved.

Table 1. Scope of the Suzuki–Miyaura reaction.^[a]
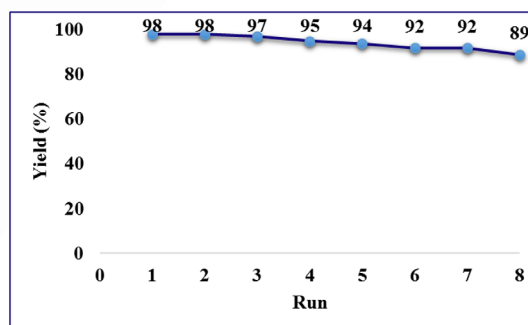
$$\text{Ar}^1\text{X} + \text{Ar}^2\text{B}(\text{OH})_2 \xrightarrow[\text{RT or 80 } ^\circ\text{C}]{\text{Catalyst (0.22 mol\% Pd), K}_2\text{CO}_3, \text{EtOH:H}_2\text{O}} \text{Ar}^1\text{-Ar}^2$$

Entry	Ar ¹ X	Ar ² B(OH) ₂	t [h]	T [°C]	Product	Yield [%] ^[b]
1		PhB(OH) ₂	2	30		98
2		PhB(OH) ₂	1	30		100
3		PhB(OH) ₂	24	30		98
4		PhB(OH) ₂	12	30		93
5			24	30		92
6		PhB(OH) ₂	24	30		93
7		PhB(OH) ₂	24	30		97
8			24	30		87
9		PhB(OH) ₂	1	30		97
10		PhB(OH) ₂	24	30		88
11		PhB(OH) ₂	1	30		88
12		PhB(OH) ₂	24	30		95
13		PhB(OH) ₂	18	30		93
14			12	30		91
15			5	30		93
16		PhB(OH) ₂	24	30		95
17			2	30		96
18		PhB(OH) ₂	36	80		70
19		PhB(OH) ₂	36	80		47
20		PhB(OH) ₂	36	60		66
21			36	80		71
22		PhB(OH) ₂	36	80		88

[a] Reaction conditions: aryl halide (1 mmol), arylboronic acid (1.5 mmol), K₂CO₃ (1.5 mmol), solvent (2 mL), catalyst (0.22 mol% Pd). [b] Isolated yield.

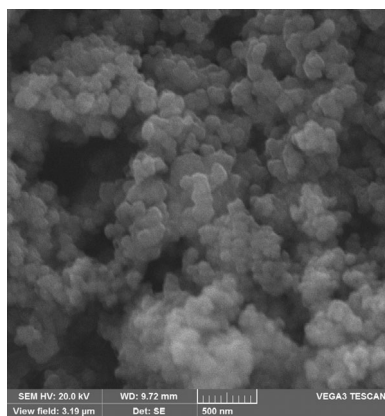


Figure 13. SEM image of the catalyst after the third run.

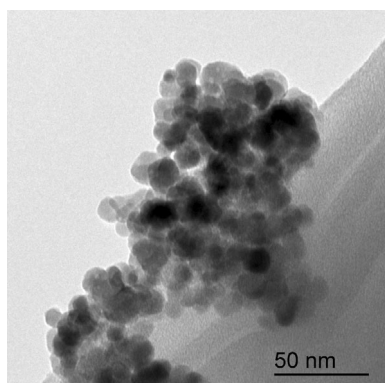


Figure 14. TEM image of reused catalyst after the third run.

Furthermore, a study of the magnetization of the recycled catalyst after the third run (Figure 9) confirmed the preservation of the superparamagnetic properties of the catalyst during the reaction.

Conclusions

We have introduced a new magnetically separable Pd catalyst, in which magnetic Fe_3O_4 was modified by carbon dots as a green and abundant material to support Pd nanoparticles (NPs). The new material can reduce PdCl_2 to Pd NPs without the use of another reducing agent. The obtained catalyst was characterized successfully by different techniques, such as energy-dispersive spectroscopy, TEM, thermogravimetric analysis, FTIR spectroscopy, vibrating sample magnetometry, atomic absorption spectroscopy, and solid UV/Vis spectroscopy, and has been applied successfully as an efficient catalyst for the Suzuki–Miyaura cross-coupling reaction in aqueous media (aqueous ethanol). The exact amount of required catalyst and type of solvent and base were determined using design of experiments. The reactions of aryl bromides were performed at room temperature, and that of aryl chlorides at 80°C . Comparative studies with physically adsorbed Pd on Fe_3O_4 NPs showed a very low catalytic efficiency with respect to $\text{Pd@C-dots@Fe}_3\text{O}_4$. The catalyst was recycled easily using a magnetic

bar in eight consecutive runs ■■ with no significant loss of ■■ catalytic activity and its structure and the superparamagnetic properties were retained.

Experimental Section

Synthesis of magnetic NPs^[14]

$\text{FeCl}_3\cdot 6\text{H}_2\text{O}$ (11.0 g) and $\text{FeCl}_2\cdot 4\text{H}_2\text{O}$ (4.0 g) were dissolved in deionized water (250 mL) and the mixture was stirred using a mechanical stirrer under an Ar atmosphere. To the resulting mixture, aqueous ammonia (25%, 40 mL) was added slowly over 20 min, and the mixture was stirred at 80°C for 4 h. A black precipitate of Fe_3O_4 was collected by using an external magnet and washed with deionized water (3×20 mL) and ethanol (3×20 mL) and finally dried under vacuum.

Synthesis of carbon-dots-modified Fe_3O_4

Citric acid (1 g) and urea (0.5 g) were dissolved in distilled water (25 mL), and the mixture was transferred to a Teflon autoclave and heated at 160°C for 6 h. Then, the reactor was cooled to RT, and the obtained material was centrifuged at 10000 rpm for 10 min to remove larger particles. Fe_3O_4 NPs (0.5 g) were sonicated in water (5 mL) for 15 min. Then, the C-dots suspension (0.7 mL) was added to the flask that contained the magnetic particles, and this mixture was stirred mechanically for 24 h at 60°C . The resulting carbon-dots-modified Fe_3O_4 was subjected to magnetic separation and the obtained material was washed with deionized water (3×10 mL) and ethanol (3×10 mL) and dried under vacuum.

Synthesis of $\text{Pd@C-dots@Fe}_3\text{O}_4$

C-dots@ Fe_3O_4 (500 mg) was sonicated in water (10 mL) for 30 min at RT. In another flask, PdCl_2 (60 mg) was sonicated and dissolved in water (5 mL). Then, the solution of PdCl_2 was added to the flask that contained C-dots@ Fe_3O_4 , and the mixture was mechanically stirred for 24 h at 60°C under reflux. Then, the solid was separated magnetically, washed with water (3×20 mL) and ethanol (3×20 mL), and dried in an oven at 60°C . The loading of Pd on the obtained material was determined by ICP analysis to be 0.275 mmol g^{-1} .

General procedure for the Suzuki–Miyaura reaction

Aryl halide (1 mmol), arylboronic acid (1.5 mmol), K_2CO_3 (1.5 mmol), catalyst (8 mg that contained 0.22 mol% Pd) and water/ethanol (1:1, 2 mL) were added to a 5 mL flask, and the mixture was stirred mechanically at RT or 80°C (depending on the aryl halide). The progresses of the reactions were monitored by GC. After completion of the reaction, the crude product was extracted using ethyl acetate. The pure products were obtained by column chromatography on silica using the hexane and ethyl acetate as eluent.

Acknowledgements

The authors are grateful to the Institute for Advanced Studies in Basic Sciences (IASBS) and the Iran National Science Foundation (INSF-Grant number of 94010666) for support of this work. C.N. is grateful to the Spanish Ministerio de Economía y Competitividad (MINECO) (projects CTQ2013-43446-P and CTQ2014-51912-REDC),

FEDER, the Generalitat Valenciana (PROMETEOII/2014/017), and the University of Alicante for financial support.

Keywords: cross-coupling · iron · nanoparticles · palladium · quantum dots

- [1] a) Á. Molnár, *Palladium-Catalyzed Coupling Reactions: Practical Aspects, Future Developments*, Wiley-VCH, Weinheim, **2013**; b) Á. Molnár, *Chem. Rev.* **2011**, *111*, 2251–2320; c) R. Jana, T. P. Pathak, M. S. Sigman, *Chem. Rev.* **2011**, *111*, 1417–1492; d) M. Lamblin, L. Nassar-Hardy, J. C. Hierso, E. Fouquet, F. X. Felpin, *Adv. Synth. Catal.* **2010**, *352*, 33–79; e) B. C. G. Söderberg, *Coord. Chem. Rev.* **2003**, *241*, 147–247; f) A. Fihri, M. Bouhrara, B. Nekoueishahraki, J.-M. Basset, V. Polshettiwar, *Chem. Soc. Rev.* **2011**, *40*, 5181–5203; g) V. Polshettiwar, A. Decottignies, C. Len, A. Fihri, *ChemSusChem* **2010**, *3*, 502–522.
- [2] a) M. Pagliaro, V. Pandarus, F. Béland, R. Ciriminna, G. Palmisano, P. Demma Carà, *Catal. Sci. Technol.* **2011**, *1*, 736–739; b) C. J. Pink, H.-t. Wong, F. C. Ferreira, A. G. Livingston, *Org. Process Res. Dev.* **2008**, *12*, 589–595; c) Y. Yabe, Y. Sawama, Y. Monguch, H. Sajiki, *Catal. Sci. Technol.* **2014**, *4*, 260–271; d) M. Mora, C. Jiménez-Sanchidrián, J. R. Ruiz, *Curr. Org. Chem.* **2012**, *16*, 1128–1150; e) L. Yin, J. Liebscher, *Chem. Rev.* **2007**, *107*, 133–173; f) M. Pagliaro, V. Pandarus, R. Ciriminna, F. Béland, P. Demma Carà, *ChemCatChem* **2012**, *4*, 432–445.
- [3] a) V. Polshettiwar, A. Molnár, *Tetrahedron* **2007**, *63*, 6949–6976; b) A. Fihri, D. Cha, M. Bouhrara, N. Almana, V. Polshettiwar, *ChemSusChem* **2012**, *5*, 85–89.
- [4] a) S. Navalón, M. Álvaro, H. García, *ChemCatChem* **2013**, *5*, 3460–3480; b) Y. Gong, M. Li, H. Li, Y. Wang, *Green Chem.* **2015**, *17*, 715–736.
- [5] a) B. Karimi, H. Behzadnia, H. Vali, *ChemCatChem* **2014**, *6*, 745–748; b) R. Ali Molla, M. A. Iqbal, K. Ghosh, A. S. Roy, Kamaluddin, S. M. Islam, *RSC Adv.* **2014**, *4*, 48177–48190; c) P. Puthiaraj, K. Pitchumani, *Green Chem.* **2014**, *16*, 4223–4233; d) H. Veisi, A. Amini Manesh, N. Eivazi, A. R. Faraji, *RSC Adv.* **2015**, *5*, 20098–20107.
- [6] a) F. Bellina, C. Chiappe, *Molecules* **2010**, *15*, 2211–2245; b) S. B. Park, H. Alper, *Chem. Commun.* **2004**, 1306–1307; c) N. Iranpoor, H. Firouzabadi, Y. Ahmadi, *Eur. J. Org. Chem.* **2012**, *2012*, 305–311; d) P. Nehra, B. Khungar, K. Pericherla, S. C. Sivasubramaniana, A. Kumar, *Green Chem.* **2014**, *16*, 4266–4271.
- [7] a) A. Ghaderi, M. Gholinejad, H. Firouzabadi, *Curr. Org. Chem.* **2015**, *19*, 1–22; b) A. Hassine, M. Bouhrara, S. Sebti, A. Solhy, R. Mahfouz, D. Luat, C. Len, A. Fihri, *Curr. Org. Chem.* **2014**, *18*, 3141–3148.
- [8] a) B. Karimi, F. Mansouri, H. Mirzaei, *ChemCatChem* **2015**, *7*, 1736–1789; b) H. Veisi, J. Gholami, H. Ueda, P. Mohammadi, M. Noroozi, *J. Mol. Catal. A* **2015**, *396*, 216–223; c) S. Verma, D. Verma, A. K. Sinha, S. L. Jain, *Appl. Catal. A* **2015**, *489*, 17–23; d) Z. Yinghui, S. C. Peng, A. Emi, S. Zh. Monalisa, R. A. Kemp, *Adv. Synth. Catal.* **2007**, *349*, 1917–1922; e) C. G. Tan, R. N. Grass, *Chem. Commun.* **2008**, 4297–4299; f) S. Shylesh, L. Wang, W. R. Thiel, *Adv. Synth. Catal.* **2010**, *352*, 425–432.
- [9] S. Y. Lim, W. Shen, Z. Gao, *Chem. Soc. Rev.* **2015**, *44*, 362–381.
- [10] Y. Wang, A. Hu, *J. Mater. Chem. C* **2014**, *2*, 6921–6939.
- [11] a) R. Kannan, H.-R. Jang, E.-S. Yoo, H.-K. Lee, D. J. Yoo, *RSC Adv.* **2015**, *5*, 35993–36000; b) X. Wu, S. Gua, J. Zhang, *Chem. Commun.* **2015**, *51*, 6318–6321; c) X. Wang, L. Wang, F. Zhao, C. Hu, Y. Zhao, Z. Zhang, S. Chen, G. Shi, L. Qu, *Nanoscale* **2015**, *7*, 3035–3042; d) Ch.-Ch. Wang, S.-Y. Lu, *Nanoscale* **2015**, *7*, 1209–1215; e) H. Li, C. Sun, M. Ali, F. Zhou, X. Zhang, D. R. MacFarlane, *Angew. Chem. Int. Ed.* **2015**, *54*, 8420–8424; *Angew. Chem.* **2015**, *127*, 8540–8544; f) S. Liu, J. Tian, L. Wang, Y. Luo, X. Sun, *RSC Adv.* **2012**, *2*, 411–413; g) A. Ohtaka, J. M. Sansano, C. Nájera, I. M. García, Á. Berenguer-Murcia, D. Cazorla-Amorós, *ChemCatChem* **2015**, *7*, 1841–1847.
- [12] D. Dey, T. Bhattacharya, B. Majumdar, S. Mandani, B. Sharma, T. K. Sarma, *Dalton Trans.* **2013**, *42*, 13821–13825.
- [13] a) H. Firouzabadi, N. Iranpoor, M. Gholinejad, J. Hoseini, *Adv. Synth. Catal.* **2011**, *353*, 125–132; b) H. Firouzabadi, N. Iranpoor, M. Gholinejad, S. Akbar, N. Jeddi, *RSC Adv.* **2014**, *4*, 17060–17070; c) M. Gholinejad, M. Razeghi, C. Nájera, *RSC Adv.* **2015**, *5*, 49568–49576; d) M. Gholinejad, J. Ahmadi, *ChemPlusChem* **2015**, *80*, 973–979; e) M. Gholinejad, A. Amiranfar, *J. Mol. Catal. A* **2015**, *397*, 106–113; f) M. Gholinejad, B. Karimi, F. Mansouri, *J. Mol. Catal. A* **2014**, *386*, 20–26; g) M. Gholinejad, H. Firouzabadi, *New J. Chem.* **2015**, *39*, 5953–5959.
- [14] R. Massart, *IEEE Trans. Magn.* **1981**, *17*, 1247–1248.
- [15] a) X. M. Li, S. L. Zhang, S. A. Kulinich, Y. L. Liu, H. B. Zeng, *Sci. Rep.* **2014**, *4*, 4976; b) S. Liu, J. Tian, L. Wang, Y. Zhang, X. Qin, Y. Luo, A. M. Asiri, A. O. Al-Youbi, X. P. Sun, *Adv. Mater.* **2012**, *24*, 2037–2041.
- [16] S. Li, W. Zhang, M.-H. So, C.-M. Che, R. Wang, R. Chen, *J. Mol. Catal. A* **2012**, *359*, 81–87.
- [17] M. Gholinejad, F. Hamed, P. Biji, *Dalton Trans.* **2015**, *44*, 14293–14303.
- [18] a) K. K. R. Datta, M. Eswaramoorthy, C. N. R. Rao, *J. Mater. Chem.* **2007**, *17*, 613–615; b) H. Firouzabadi, N. Iranpoor, A. Ghaderi, M. Gholinejad, S. Rahimi, S. Jokar, *RSC Adv.* **2014**, *4*, 27674–27682.
- [19] J. Sun, Y. Fu, G. He, X. Sun, X. Wang, *Catal. Sci. Technol.* **2014**, *4*, 1742–1748.
- [20] a) V. K. Aggarwal, A. C. Staubitz, M. Owen, *Org. Process Res. Dev.* **2006**, *10*, 64–69; b) K. B. Sidhpuria, A. L. Daniel-da-Silva, T. Trindade, J. A. P. Coutinho, *Green Chem.* **2011**, *13*, 340–349.

Received: August 18, 2015


Published online on ■■■■■, 0000

FULL PAPERS

M. Gholinejad,* M. Seyedhamzeh,
M. Razeghi, C. Najera,*
M. Kompany-Zareh

■ ■ - ■ ■

Iron Oxide Nanoparticles Modified with Carbon Quantum Nanodots for the Stabilization of Palladium Nanoparticles: An Efficient Catalyst for the Suzuki Reaction in Aqueous Media under Mild Conditions

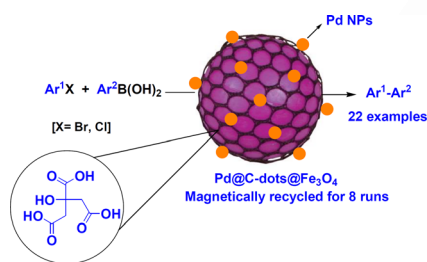

Dot to dot: Pd supported on Fe₃O₄ nanoparticles modified with carbon quantum nanodots is shown to be an efficient catalyst for Suzuki coupling reactions.



Modified iron oxide nanoparticles stabilize Pd nanoparticles for #catalysis @UA Universidad **SPACE RE-**
SERVED FOR IMAGE AND LINK

Share your work on social media! *ChemCatChem* has added Twitter as a means to promote your article. Twitter is an online microblogging service that enables its users to send and read text-based messages of up to 140 characters, known as “tweets”. Please check the pre-written tweet in the galley proofs for accuracy. Should you or your institute have a Twitter account, please let us know the appropriate username (i.e., @accountname), and we will do our best to include this information in the tweet. This tweet will be posted to the journal’s Twitter account @ChemCatChem (follow us!) upon online publication of your article, and we recommended you to repost (“retweet”) it to alert other researchers about your publication.

Please check that the ORCID identifiers listed below are correct. We encourage all authors to provide an ORCID identifier for each coauthor. ORCID is a registry that provides researchers with a unique digital identifier. Some funding agencies recommend or even require the inclusion of ORCID IDs in all published articles, and authors should consult their funding agency guidelines for details. Registration is easy and free; for further information, see <http://orcid.org/>.

Mohammad Gholinejad
Mohammed Seyedhamzeh
Mehran Razeghi
Carmen Najera
Mohsen Kompany-Zareh