

## Accepted Manuscript

Title: Pt/carbon nanofibers electrocatalysts for fuel cells.  
Effect of the support oxidizing treatment

Authors: F. Zaragoza-Martín, D. Sopeña-Escario, E. Morallón,  
C. Salinas-Martínez de Lecea



PII: S0378-7753(07)01362-6  
DOI: doi:10.1016/j.jpowsour.2007.06.078  
Reference: POWER 9529

To appear in: *Journal of Power Sources*

Received date: 26-2-2007  
Revised date: 12-6-2007  
Accepted date: 17-6-2007

Please cite this article as: F. Zaragoza-Martín, D. Sopeña-Escario, E. Morallón, C. Salinas-Martínez de Lecea, Pt/carbon nanofibers electrocatalysts for fuel cells. Effect of the support oxidizing treatment, *Journal of Power Sources* (2007), doi:10.1016/j.jpowsour.2007.06.078

This is a PDF file of an unedited manuscript that has been accepted for publication. As a service to our customers we are providing this early version of the manuscript. The manuscript will undergo copyediting, typesetting, and review of the resulting proof before it is published in its final form. Please note that during the production process errors may be discovered which could affect the content, and all legal disclaimers that apply to the journal pertain.

**Pt/CARBON NANOFIBERS ELECTROCATALYSTS FOR FUEL CELLS.****EFFECT OF THE SUPPORT OXIDIZING TREATMENT**F. Zaragoza-Martín<sup>a</sup>, D. Sopeña-Escario<sup>b</sup>, E. Morallón<sup>c</sup> andC. Salinas-Martínez de Lecea<sup>a</sup><sup>a</sup>Departamento de Química Inorgánica. Universidad de Alicante. Apartado 99. E-03080 Alicante (Spain)<sup>b</sup>Fundación CIDAUT. Parque tecnológico de Boecillo. E-47151 Boecillo (Valladolid). Spain.<sup>c</sup>Departamento de Química Física e Instituto Universitario de Materiales. Universidad de Alicante. Apartado 99. E-03080 Alicante (Spain)**Abstract**

Different Pt-based electrocatalysts supported on carbon nanofibers and carbon black (Vulcan XC-72R) have been prepared using a polymer-mediated synthesis. The electrocatalysts have been characterized by transmission electron microscopy (TEM), X-ray diffraction (XRD) and cyclic voltammetry. The effect of carbon nanofibers treatment with HNO<sub>3</sub> solution on Pt particle size and electroactive area has been analyzed. Highly dispersed Pt with homogeneous particle size and an electroactive area around of 100 m<sup>2</sup> g<sup>-1</sup> is obtained in raw carbon nanofibers. The oxidizing treatment of the carbon nanofibers produces agglomeration of the platinum nanoparticles and an electroactive area of 53 m<sup>2</sup> g<sup>-1</sup>. Durability studies indicate a decrease of 14% in the electroactive area after 90h at 1.2V in 0.5M H<sub>2</sub>SO<sub>4</sub> for platinum supported on raw carbon nanofibers and Vulcan XC-72R. The electrocatalyst supported on oxidized carbon nanofibers are stable under similar conditions.

Corresponding author

E. Morallón

[morallon@ua.es](mailto:morallon@ua.es)

Telf. 34-965909590

Fax: 34-965903537

## 1. Introduction

Low-temperature fuel cells, using either hydrogen or methanol as feed, are an efficient alternative to combustion engines in the means of transport. An important factor in the fuel cells commercialization is the catalyst cost. This cost has been reduced by using carbon supported platinum; however, more efforts have to be done in the development of more efficient catalysts with a smaller load in precious metal. It is recognised that the form of carbon can affect the dispersion of the Pt particles [1-3]. Carbon nanofibers are such an important carbon form in the industry, and the study of the platinum dispersion on this material and its comparison with carbon black may lead to the development of improved electrocatalysts. The catalytic nanoparticles on the external walls of the carbon nanofibers (as in the case of carbon nanotubes) are easier to react with the fuel than those in the inter-particle pores of carbon black [2,4,5].

In the last decade, carbon nanotubes CNTs and nanofibers CNFs have been proposed as Pt supports for proton exchange membrane fuel cells [6-10] and direct methanol fuel cells [10-14]. Frequently, CNTs and CNFs were treated with  $\text{HNO}_3$  acid or  $\text{H}_2\text{SO}_4\text{-HNO}_3$  mixed acids for purification or functionalization [6,8,11]. The functionalization produces high density of oxygen-containing species on the CNT surface. The results of electrocatalytic activity in oxygen reduction reaction for Pt/CNT catalysts showed a positive effect of the functionalization [6]. Surface modifications of MWNTs (multiwalled carbon nanotubes) were found to be a key factor in controlling the particle size and distribution of Pt particles deposited on the MWNT support [11].

Recently, the effect of carbon supports treatment with oxidative acids in the electro-catalytic oxidation of  $\text{H}_2$  [15] and  $\text{CO}$  [15, 16] has been investigated. Treating carbon Vulcan XC-72R with  $\text{HNO}_3$  [15], an enhancement of the amount of oxygen groups was observed. However, neither large amount of Pt, nor better Pt dispersion was

observed during the preparation of Pt/C samples. Li et al. [16] observed a wider Pt size distribution for CNTs treated with HNO<sub>3</sub> acid in comparison to the as received CNTs.

The objective pursued in this work was to prepare platinum-based electrocatalysts using carbon nanofibers as support. For comparative purposes electrocatalysts prepared with carbon black (Vulcan XC-72R) as support has been carried out. Furthermore, the effect of the oxidising treatment with HNO<sub>3</sub> of the carbon nanofibers on the metal dispersion and catalytic activity for hydrogen oxidation has been investigated.

## 2. Experimental

### 2.1. Materials

The materials used were: hexachloroplatinic acid (H<sub>2</sub>PtCl<sub>6</sub>·H<sub>2</sub>O), sulfuric acid 98%, nitric acid 65%, hydrochloric acid 37%, ethylenglycol, polivinylpirrolidone (PVP) AW 40,000, Nafion solution (5% w/w) from Aldrich, carbon black (Vulcan XC-72R) supplied by Cabot Corporation and carbon nanofibers supplied by Grupo Antolin. Water used in this work was obtained from a PureLab Elga purifier with a resistivity of 18 MΩ cm.

### 2.2. Carbon nanofibers treatments

Original carbon nanofibers were treated at 500 °C in N<sub>2</sub> flow (200 mLmin<sup>-1</sup>g<sup>-1</sup>) during 3 h (sample denoted NF). In addition, two acid treatments were conducted on NF sample.

- Soxhlet extraction with HCl 37% during 8 h, followed by washing with water in Soxhlet for 8 h (sample denoted NF1).

- Microwave treatment with nitric acid solution. 250 mg of carbon nanofibers and 10 mL HNO<sub>3</sub> 69% were heated by MW (570W) for 35 min. The sample was washed after treatment with water in Soxhlet for 8 h (sample denoted NF2).

Both treated materials were dried after treatment in a conventional oven at 120°C overnight.

### **2.3. Electrocatalysts preparation.**

The experimental procedure for the electrocatalysts preparation is based on the method described by Chen and Xing [17]. This method is a reduction-by-solvent type, which involves using PVP to achieve small and uniform platinum particles. The solvent used was an ethylene glycol-water mixture in a volume ratio 3:1. Theoretical platinum content in the catalysts was fixed in 20%. Some modifications were introduced in order to make this method suitable for carbon nanofiber supports. The support was previously dispersed in ethylene glycol, with the aim to improve the fiber-solvent contact. The Pt precursor (hexachloroplatinic acid) was added as a solution (1% wt Pt). The prepared catalyst was washed with acetone and ultra pure water instead of ethanol, since the latter may contaminate the platinum surface.

The catalysts notation is Pt/support name.

### **2.4. Characterization**

Ash content in carbon supports was determined by thermogravimetry (TG) in air (80 mL min<sup>-1</sup>) flow, heating the sample from 25°C to 920°C (heating rate: 10°C min<sup>-1</sup>) using a thermobalance Stanton Redcroft STA-780. TEM images were obtained using a JEOL microscope (model JEM-2010). The X-ray diffraction (XRD) equipment used

was a Seifer JSO-Debyeflex 2002. Temperature programmed desorption (TPD) of carbon supports were carried out using a thermobalance SDT TA Instruments 2960, coupled to a mass spectrometer Balzers MSC 200 ThermoStar (heating rate:  $20^{\circ}\text{C min}^{-1}$ ; gas flow: He,  $100\text{ mL min}^{-1}$ ).

To determine the metal content, 0.1 g of the catalyst were digested with 20 mL  $\text{H}_2\text{SO}_4$  (98%) and 10 mL  $\text{HNO}_3$  (65%). The suspension was heated at 573K (under reflux) until a clear solution was obtained (after about 24h). After solvent evaporation, 1 mL  $\text{HNO}_3$  (65%) and 3 mL  $\text{HCl}$  (37%) were added. The obtained solution was transferred into a 100ml calibrated flask and the volume completed with deionised water. The solutions were then analyzed using inductively coupled plasma atomic emission spectroscopy (ICP-AES), Perkin Elmer Optima 3000 and 4300.

X-ray photoelectron spectroscopy (XPS) of the catalysts was carried out by means of a spectrometer VG-Microtech Multilab, using  $\text{MgK}\alpha$  (1253.6 eV) radiation from a double anode with a energy flow of 50 eV.

For the cyclic voltammetry (CV) measurements a three-electrode electrochemical cell was used. The reference electrode was a reversible hydrogen electrode (RHE), whereas a spiral-rolled platinum wire was used as the counter electrode. The equipment used for the voltammetric measurements was an EG&G potentiostat (model 263A). For the voltammetric characterization, 5  $\mu\text{L}$  of dispersion of the powder samples were deposited on a glassy carbon surface of a 3 mm of diameter previously sanded and cleaned with water. The support dispersions were made using 8 mg of the carbon nanofibers and 1 mL of acetone, whereas for the catalysts dispersions in acetone and Nafion (5% w/w) solution were used. The concentration of the catalysts dispersions was 10 mg/mL, and Nafion content (as solid) was 33% of the total solid

content (catalyst + Nafion). All dispersions were homogenized in an ultrasonic bath for at least 40 min.

### 3. Results and discussion

#### 3.1. Characterization of the carbon nanofibers

Table 1 show the ash content (in weight percentage) of the carbon supports. As already known, Vulcan XC-72R has very low ash content. In carbon nanofibers, the ash content is mainly constituted by the metal compounds used in their synthesis. It can be observed that treatment with  $\text{HNO}_3$  completely removes these compounds, whereas the treatment with  $\text{HCl}$  is not so effective in metal removal. Table 1 also shows the quantification of the TPD experiments and the XPS analysis of the samples. These carbon materials contain mainly groups desorbing as  $\text{CO}_2$ . According to the literature [18] they correspond to carboxylics, lactones and anhydrides. Acid treatments modify the amount of these groups in the carbon nanofibers. The oxygen content estimated from the amount of  $\text{CO}+2\text{CO}_2$  ( $\mu\text{mol g}^{-1}$ ) is included in Table 1.  $\text{HCl}$  reduces the oxygen content while  $\text{HNO}_3$  considerably increases the oxygen surface groups. The oxygen content results from XPS again show that sample NF2 has the higher value. However, for the other samples some differences are observed in comparison to TPD results. The values for NF and NF1 are similar while sample Vulcan XC-72R having the lower value from TPD presents much higher oxygen content. The apparent discrepancy among TPD and XPS results must be a consequence of the depth limitation of XPS analysis while oxygen from TPD corresponds to the sample bulk. The differences observed from both techniques are a consequence of the different distribution of oxygen groups in the carbon materials.

The NF materials are highly graphitic, stacked-cup-type carbon nanofibers having a wide hollow core, without amorphous carbon coatings [19]. The oxidizing treatment produces oxygen groups at the edges of graphitic planes, increasing the number of defects at the surface.

Figure 1 shows the steady voltammograms obtained for the carbon supports in 0.5M H<sub>2</sub>SO<sub>4</sub> solutions. As it can be seen, samples NF, NF1 and Vulcan XC-72R mainly show capacitive behaviour when cycling between -0.3 and 1.2 V (dotted lines in Figures 1a, 1b and 1d). In the case of sample NF2, in the same potential range, shows a clear reversible peak around 0.65V related to the existence of oxygen surface groups as consequence of the HNO<sub>3</sub> treatment. When cycling up to 1.6 V, the steady voltammograms of samples NF and NF1 change becoming similar to that of NF2, since surface oxygen groups are being created due to electrochemical oxidation. The voltammogram for Vulcan XC-72R support also shows an increase in the current after oxidation up to 1.6V, but this increase is lower than for the NF and NF1 samples. Contrarily, when the potential increases to 1.6V, the voltammogram shape of sample NF2 does not change significantly showing the redox couple in the same potential range. Then, the electrochemical treatment in NF2 sample does not produce additional surface oxygen groups at these conditions.

Then, the characterization of the carbon nanofibers indicates that HCl acid removes most metal content without creating surface groups. HNO<sub>3</sub> acid treatment provides the formation of oxygen surface groups as well as removal of the initial metal content, the important amount of surface oxygen groups producing the redox processes in the voltammogram. NF1 and NF samples show a very similar electrochemical behaviour.



## 3.2. Characterization of the Pt electrocatalysts.

### 3.2.1. Physicochemical characterization

Figure 2 shows the TEM images of the different Pt electrocatalysts showing a uniform distribution of the platinum particles on the carbon surface. Pt particles are also very uniform in size. However, as observed in Figure 2c the metal particles in sample Pt/NF2, although not very different in diameter compared to other samples, are agglomerated forming long clusters. The metal particle size distribution in the supported catalysts was obtained by measuring the size of ~1000 randomly chosen particles in the magnified TEM images. For sample Pt/NF2, considering the particular shape of the clusters, the criterion used for particle sizing was the average of diameter and length. Figure 3 shows the histograms obtained for the four platinum supported catalysts. The average diameters obtained (included in Table 2) are 3.4, 2.7 and 2.6 nm for Pt/NF, Pt/NF1 and Pt/Vulcan XC-72R respectively, which are accompanied by a relatively narrow particle size distribution (1-5nm). The polymer mediated synthesis [17] facilitates the formation of small and uniform Pt particles on the different carbon nanofibers supports. However, for the Pt/NF2 catalyst the average size is larger and also the particle size distribution is wider than for the other supports. Figure 4 shows the powder XRD patterns for the different platinum supported electrocatalysts. The clear diffraction peak at  $26.3^\circ$  in carbon nanofibers is associated with the (002) graphitic planes. The graphitic structure of the carbon nanofibers wall is also observed in the micrograph of Fig. 2b). Contrarily, the crystallinity of sample Vulcan XC-72R is very poor. All the electrocatalysts display the characteristic patterns of Pt fcc diffraction. The  $2\theta$  values of the (111), (100) and (110) peaks appear at around  $39.6^\circ$ ,  $46.0^\circ$  and  $67.7^\circ$  respectively for all the catalysts. The broader diffraction peaks for the Pt/NF, Pt/NF1 and Pt/Vulcan XC-72R led to smaller average particle size as calculated by the Scherrer

equation [20]. Table 2 compares the estimated average size of the platinum particles for the different electrocatalysts obtained by TEM and DRX. The values obtained with both techniques are in good agreement with the exception of sample Pt/NF2. As stated previously, the method used for TEM particle sizing in this sample introduces some arbitrary decisions resulting in the impossible comparison with average crystal size from XRD. In any case, XRD confirms that the platinum particle size is higher for the Pt/NF2 catalyst. Thus, the oxidizing treatment with  $\text{HNO}_3$  facilitates the platinum nanoparticles agglomeration. As already mentioned the oxidizing treatment produces oxygen groups and creates defects at the surface of the carbon nanofibers. The surface oxygen groups or defects on the carbon nanofibers surface probably act as anchorage sites for Pt particles. The long clusters observed in catalyst Pt/NF2 must be a consequence of the surface oxygen groups or defects distribution at the nanofibers surface. A similar effect can be found in the literature, although this fact is not mentioned by the authors [16]. Pt supported in multi-wall carbon nanotubes treated in  $\text{HNO}_3$  and  $\text{H}_2\text{SO}_4 + \text{HNO}_3$  solutions exhibit agglomeration of Pt particles not present in the as received CNTs.

XPS has been used to determine the surface oxidation states of the platinum. Table 3 shows the percentage of Pt and Pt(II) detected in the metal surface. As it can be seen, some amount of oxidized platinum was found in all samples. This fact is not unusual as the samples were prepared and dried in air. When comparing these values with those for the particle size, it can be seen that the percentage of Pt(II) increases when the particle size decreases. Table 3 also shows the amount of platinum measured by ICP showing that the amount of platinum in all the samples is around 20-weight % in agreement with the theoretical amount in the sample preparation.

### 3.2.2. Electrochemical characterization

Figure 5 shows the steady voltammograms for the different electrocatalysts in 0.5M H<sub>2</sub>SO<sub>4</sub> solutions. It can be clearly observed the characteristic profile for a platinum electrode in the potential range between 0.05 and 0.4V, corresponding to the adsorption-desorption processes (hydrogen and anion adsorption-desorption) on the platinum surface, and in the potential range between 0.75 to 1.2V corresponding to the formation of surface platinum oxide. The electrical charge measured between 0.05-0.4V can be used (after doing the double layer correction) for the determination of the surface active area of platinum considering that the value of 210  $\mu\text{C cm}^{-2}$  corresponds to the adsorption of one electron per surface platinum atom. Table 3 shows the platinum electroactive surface area ( $S_{\text{Pt}}$ ) of the catalysts referred to the grams of platinum. The results are very similar for samples Pt/NF, Pt/NF1 and Pt/Vulcan XC-72R which have an electroactive area of  $91 \pm 5 \text{ m}^2 \text{ g}^{-1} \text{ Pt}$ . This value is among the higher found in the literature [10,16,17]. However, sample Pt/NF2 shows much lower electroactive area (nearly half of that for sample Pt/NF1).

The platinum particle size in nanometres (diameter, nm) can be calculated from the electroactive surface area ( $S_{\text{Pt}}$ ) assuming that this value is the ratio between the area and the weight of one Pt particle of spherical shape (equation 1):

$$d = \frac{6000}{\rho_{\text{Pt}} \times S_{\text{Pt}}} \quad (1)$$

where  $\rho_{\text{Pt}}$  is the platinum density ( $21.4 \text{ g}\cdot\text{cm}^{-3}$ ).

The values obtained from the voltammetric results are presented in Table 2. A very good agreement exists between the particle size obtained from cyclic voltammetry the other two techniques (TEM and DRX), showing that the electroactive surface area has been properly measured and no contamination of the platinum surface exists.

### 3.2.3. Stability test.

The electrocatalysts have been tested at 1.2V during long period time in 0.5M H<sub>2</sub>SO<sub>4</sub> solution. Figure 6 shows the electroactive surface area determined by cyclic voltammetry plotted against the time at 1.2V. It can be observed that the Pt/Vulcan XC-72R and Pt/NF catalysts show a very similar behaviour with a decrease of 14% after 90 hours. The electroactive surface area of Pt/NF1 decreases a 19 % after 75 hours. The Pt/NF2 catalyst shows a better stability than the others catalysts however its electroactive surface area is considerably lower. The results obtained for us are better than those obtained for other authors in the same conditions using carbon black and carbon nanotubes as catalysts supports [21]. This authors show a decrease of 35.2% and 20.2% for the Pt/Vulcan XC-72 and Pt/CNTs respectively after 95 h in the same experimental conditions. The decrease in the electroactive area can be ascribed to several factors like Pt particle size growth, the oxidation of the carbon support, and Pt dissolving into the solution. The TEM images (Figure 7) show a sintering of the platinum particles as the main reason of the decrease in the electroactive surface area. Then, the oxidation of the carbon support by electrochemical treatment favours the platinum nanoparticles aggregation. Then, for electrocatalysts supported on carbon nanofibers a direct relation is found between stability and oxygen content of the support (see Table 1). The lower stability is for sample Pt/NF1 while the highest is for Pt/NF2.

## 4. Conclusions.

A polymer mediated synthesis of platinum nanoparticles supported on carbon nanofibers have been used for the electrocatalysts preparation. Several techniques have been used for the characterization of the support and the electrocatalysts. This synthesis

method produces highly dispersed Pt nanoparticles on the carbon nanofibers with an average diameter around 2.5 nm. The electroactive surface areas obtained with the nanofiber supports (NF and NF1) are similar to that obtained with carbon black (Vulcan XC-72R) and near to  $100 \text{ m}^2 \text{ g}_{\text{Pt}}^{-1}$ . However, the oxidizing treatment of the nanofibers produces oxygen groups and creates defects on the carbon nanofibers acting as anchorage sites for Pt particles. Thus, the oxidizing treatment favours the aggregation of the platinum nanoparticles considerably reducing the electroactive surface area. Electrocatalysts supported on carbon nanofibers exhibits an stability at 1.2V in sulphuric acid solution similar to Pt/Vulcan XC-72R. The slight decrease in the electroactive surface area results from Pt particle aggregation that can be produced by the effect of the applied potential and the electrochemical oxidation of the carbon support.

**Acknowledgements:** The authors would like to thank Grupo Antolín Ingeniería S.A. for providing sample GANF.

## 5. References

1. A. L. Dicks, J. Pow. Sources, 156 (2006) 128-141.
2. T.R. Ralph, M.P. Hogarth, Platinum Met. Rev., 46 (3) (2002) 117-135.
3. E. Antolini, L. Giorgi, F. Cardellini, E. Passalacqua, J. Solid State. Electrochem., 5 (2001) 131-140.
4. J. Xu, K. Hua, G. Sun, C. Wang, X. Lv, Y. Wang, Electrochem. Comm., 8 (2006) 982-986.
5. D. Villers, S.H. Sun, A.M. Serventi, J.P. Dodelet, S. Désilets, J. Phys. Chem., 110 (2006) 25916-25925.

6. Z. Liu, X. Lin, J.Y. Lee, W. Zhang, M. Han, L.M. Gan, *Langmuir*, 2002, 18, 4054-4060
7. C.Wang, M. Waje, X. Wang, J.M. Tang, R. C. Haddon, Y. Yan, *Nanoletters*, 2004, 4, 345-348
8. F. Yuan, H. K. Yu, H. Ryu, *Electrochimica Acta*, 2004, 50, 685-691
9. M. Gangeri, G. Centi, A. La Malfa, S. Perathoner, R. Vieira, C. Pham-Huu, M.J. Ledoux, *Catalysis Today*, 2005, 102-102, 50-57
10. M. Carmo, V.A. Paganin, J.M. Rosolen, E.R. Gonzalez, *J. Power Sources*, 2005, 142, 169-176
11. W. Li, C. Liang, W. Zhou, J. Qiu, Z. Zhou, G. Sun, Q. Xin, *J. Phys.Chem. B* 2003, 107, 6292-6299
12. G. Che, B.B. Lakshmi, Ch. R. Martin, R. Ellen, *Langmuir*, 1999, 15(3) 750-758
13. Z. He, J. Chen, D. Liu, H. Zhou, Y. Kuang, *Diam Relat Mater*, 2004, 13, 1764-1770
14. H. Tang, J. Chen, L. Nie, D. Liu, W. Deng, Y. Kuang, S. Yao, *J. Colloid and Interface Science*, 2004), 269, 26-31
15. J. L. Gomez de la Fuente, S. Rojas, M.V. Martinez-Huertas, P. Terreros, M.A. Peña, J.L.G. Fierro, *Carbon*, 2006, 44, 1919-1929
16. L. Li, G. Wu, B-Q. Xu, *Carbon*, 2006, 44, 2973-2983
17. M. Chen, Y. Xing, *Langmuir*, 21 (2005) 9334-9338.
18. Y.Otake, R.G. Jenkins, *Carbon*, 31 (1993) 109.
19. I. Martin-Gullon, J. Vera, J. A. Conesa, J. L. González, C. Merino, *Carbon* 44 (2006) 1572-1580.
20. B.E. Warren, *X-ray Diffraction*, Addison-Wesley, Reading, MA, 1996.
21. Y. Shao, G. Yin, Y. Gao, P. Shi, *J. Electrochem. Soc.*, 153(6) (2006) A1093-A1097.

## TABLES

**Table 1.** Ash content, quantification of oxygen surface groups by TPD and XPS analysis for all carbon supports.

Carbon support	Ash (wt %)	TPD			XPS		
		CO ( $\mu\text{mol g}^{-1}$ )	CO <sub>2</sub> ( $\mu\text{mol g}^{-1}$ )	%O	%C	%O	O/C
NF	7.9	166	2603	8.6	95.6	3.8	0.04
NF1	2.6	0	1042	3.3	95.1	3.8	0.04
NF2	0	331	4512	15.0	90.8	9.2	0.10
Vulcan XC-72R	0	0	677	2.2	91.7	8.0	0.08

**Table 2.** Platinum nanoparticle sizes measured by different techniques.

Catalyst	TEM (nm)	DRX (nm)	Cyclic voltammetry (nm)
Pt/NF	3.4	2.4	3.3
Pt/NF1	2.7	2.2	2.9
Pt/NF2	5.2	3.5	5.4
Pt/Vulcan XC-72R	2.6	2.0	3.1

**Table 3.** Characterization of the different prepared Pt/carbon catalyts: Pt content by XPS and ICP and electroactive surface areas.

Catalyst	% Pt(0)	% Pt(II)	Pt (wt %) (ICP)	Electroactive surface area ( $\text{m}^2 \text{g}^{-1} \text{Pt}$ )
Pt/NF	79.6	20.4	20.6	86
Pt/NF1	72.9	27.1	20.2	96
Pt/NF2	81.5	18.5	22.1	53
Pt/Vulcan XC-72R	70.4	29.6	21.8	90

**FIGURE CAPTIONS**

**Figure 1.** Cyclic voltammogram for the different carbon supports at (-----) 1.2V and (—) 1.6V. a) NF, b) NF1, c) NF2 and d) Vulcan XC-72R. 0.5M H<sub>2</sub>SO<sub>4</sub> solution. 50 mV s<sup>-1</sup>.

**Figure 2.** TEM images of platinum nanoparticles on a) Pt/NF, b) Pt/NF1, c) Pt/NF2 and d) Pt/Vulcan XC-72R.

**Figure 3.** Histograms of Pt particle size distribution on Pt/NF, Pt/NF1, Pt/NF2 and Pt/Vulcan XC-72R catalysts.

**Figure 4.** X-Ray diffraction patterns of Pt/carbon supported catalysts.

**Figure 5.** Steady cyclic voltammograms of the different Pt/carbon catalysts at 1.2V. a) Pt/NF, b) Pt/NF1, c) Pt/NF2 and d) Pt/Vulcan XC-72R. 0.5M H<sub>2</sub>SO<sub>4</sub> solution. 50 mV s<sup>-1</sup>.

**Figure 6.** Plots of electroactive surface areas versus test time at 1.2V in 0.5M H<sub>2</sub>SO<sub>5</sub> solution for the different Pt/carbon catalysts.

**Figure 7.** TEM images after 165 h at 1.2V in 0.5M H<sub>2</sub>SO<sub>5</sub> solution for a) Pt/NF and b) Pt/Vulcan XC-72R catalysts.



## FIGURES

Figure 1

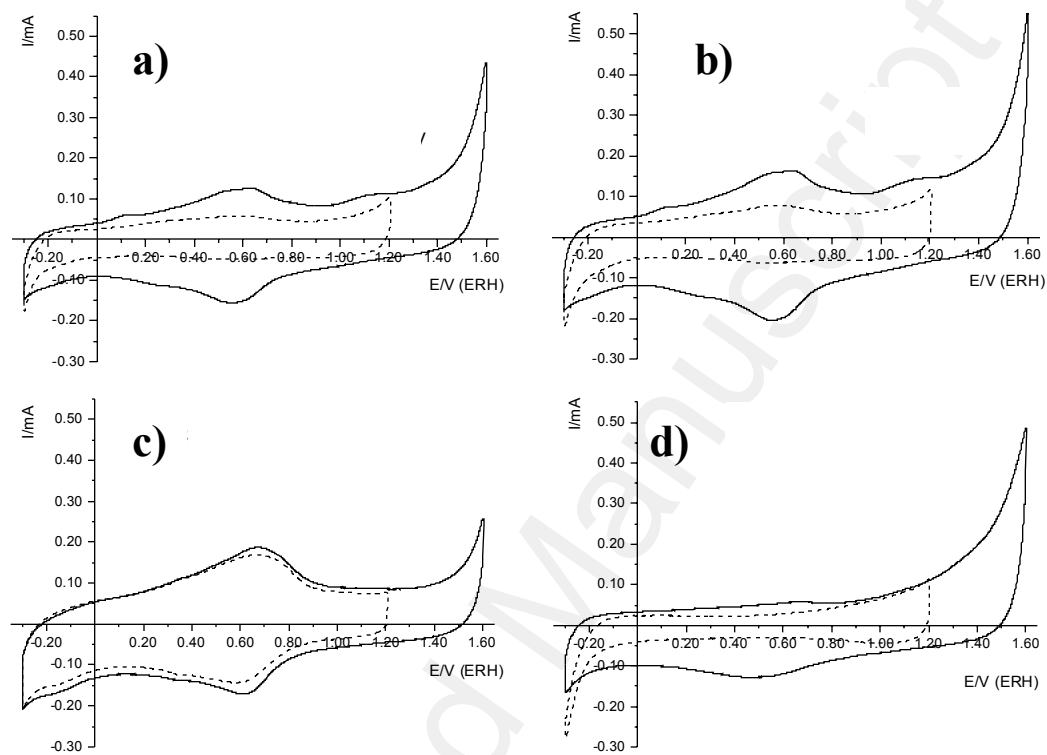


Figure 2

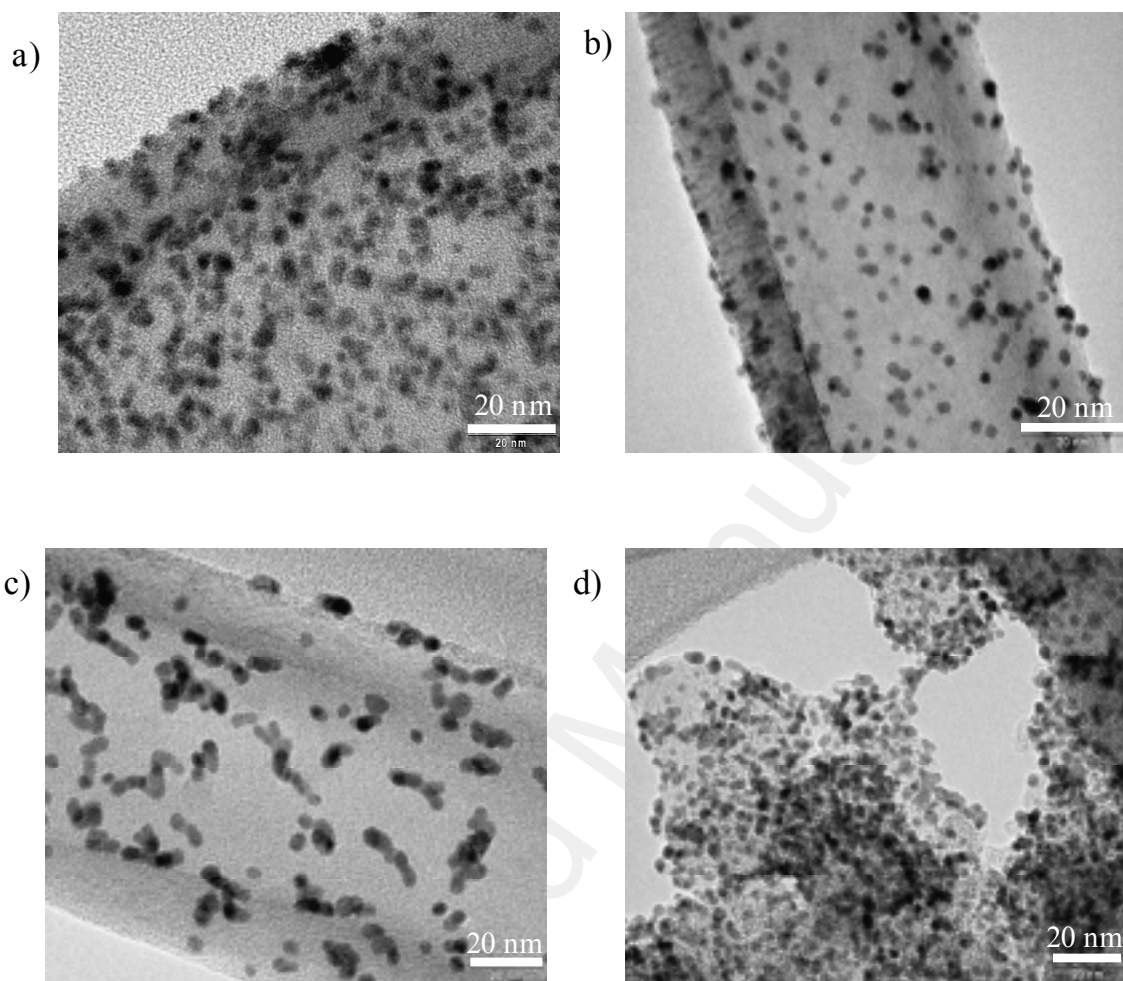


Figure 3

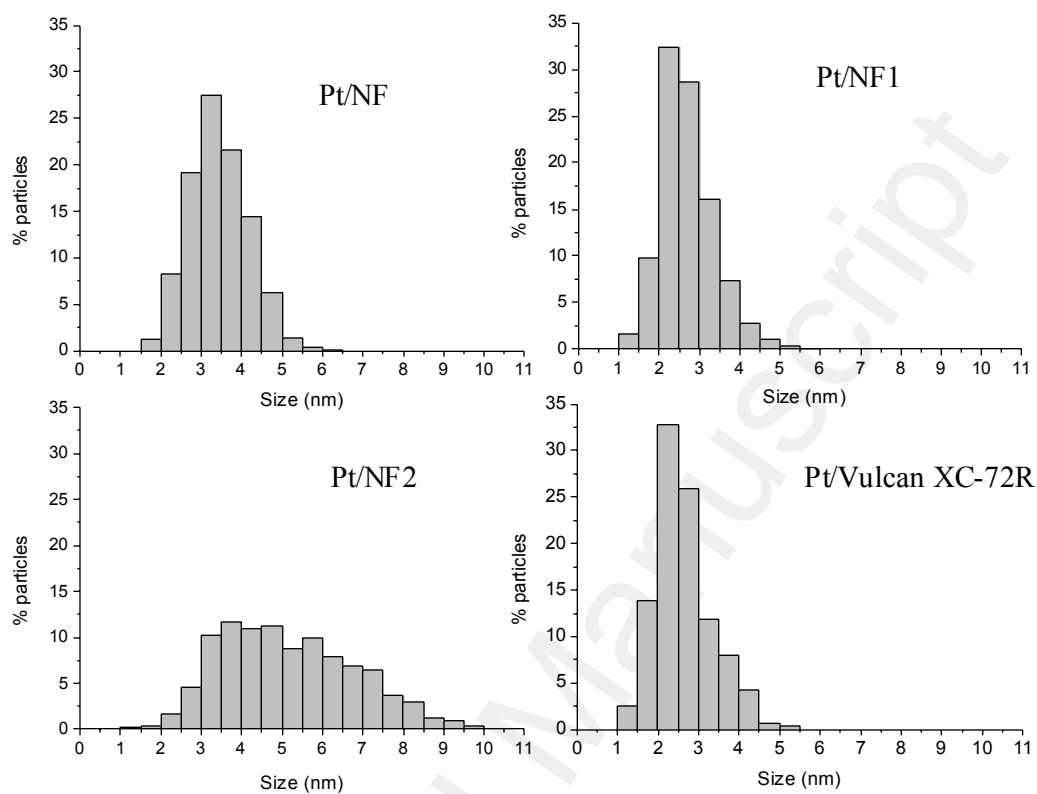


Figure 4

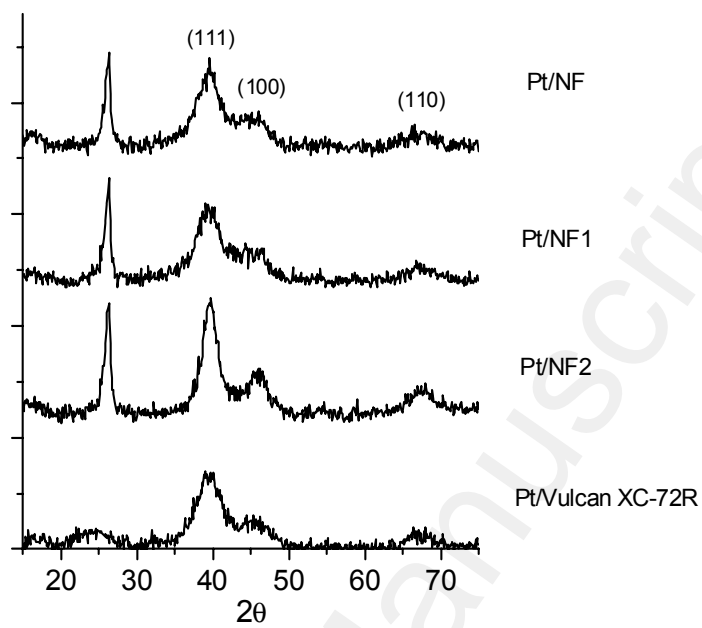


Figure 5

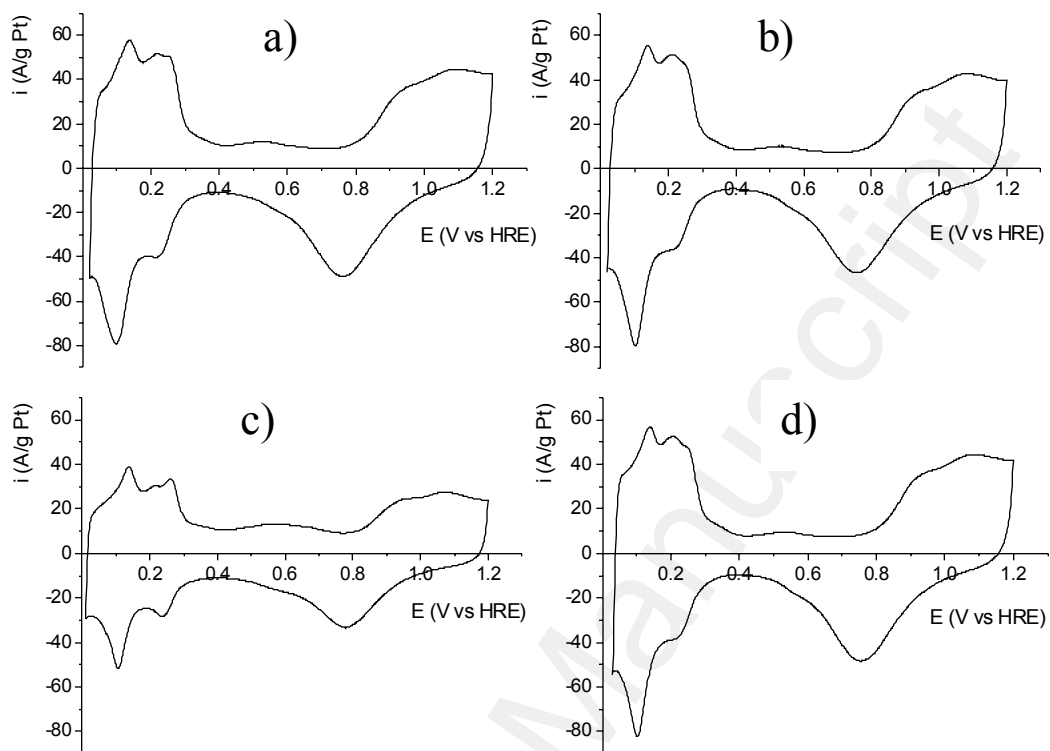
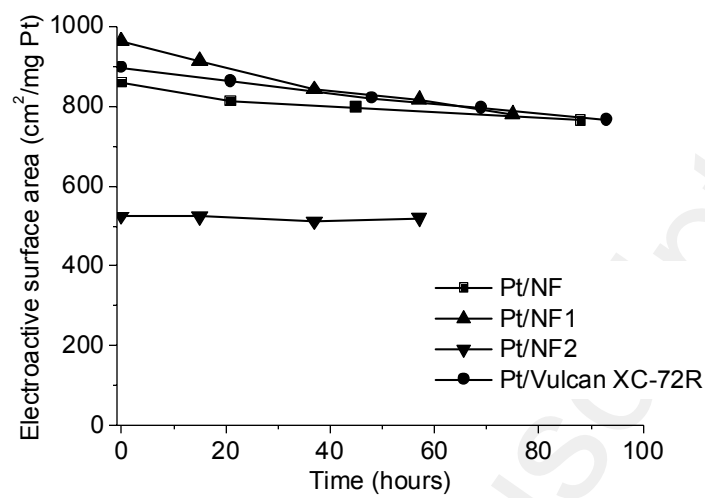


Figure 6



**Figure 7**